

AMERICAN Copyright © 2019 by American Scientific Publishers SCIENTIFIC All rights reserved.

PUBLISHERS Printed in the United States of America

ARTICLE

Magneto-Photonic Crystal Micro-Cavities in One Dimensional Photonic Crystals Fabricated by Sol Gel Process

Dermeche Nassim^{1,2}, Bouras Mounir^{1,*}, and Ahmed Kahlouche¹

In this paper, we present a study on the photonic band gap of one-dimensional photonic crystals made by SiO_2/ZrO_2 or SiO_2/TiO_2 doped with magnetic nanoparticles using the sol–gel process. The studied structure consists of a multilayer of SiO_2/ZrO_2 or SiO_2/TiO_2 and air gap with lattice constant $a=0.70~\mu m$. The structure is characterized by a background refractive index of 1.51. We started by introducing one defect at different locations, then we followed by two and three defects at different locations. The results obtained show clearly that these magnetic micro-cavities may serve as a fundamental structure in a variety of ultra-compact magneto photonic devices such as optical isolators and modulators in the future.

Keywords: Magneto Photonic, One-Dimensional Magneto-Photonic Crystals (1D MPCs), Photonic Bandgap, Micro-Cavity, Rigorous Coupled Wave Analysis (RCWA).

1. INTRODUCTION

In recent years, there had been a lot of interest magneto-photonic crystals made by sol-gel process and their potential application [1–5]. The integration of magneto-optical devices, such as isolators and circulators, remains a major challenge, due to the difficulties encountered in integrating magneto-optical materials with conventional integrated technologies. Yttrium Iron Garnet (YIG), widely used in bulk optical isolators, requires an annealing temperature of up to 700 °C to be magneto-active.

To overcome this problem, a new approach based on a magneto-optical composite matrix compatible with a glass substrate [6]. The films made by a soft chemical sol-gel process showed promising potentialities illustrated by a specific Faraday rotation of 200°/cm and an index of 1.51 (@1550 nm) [7–12]. In this way, many efforts have been made to obtain such materials compatible with the semi-conductor substrate [13, 14], but few concern the glass

In this paper, we study the effect of position and number of defects on the bandgap of 1D MPCs made by SiO₂/ZrO₂ or SiO₂/TiO₂ doped with magnetic nanoparticles using sol–gel process in different geometrical parameter configurations. We started by introducing a defect at different locations, then we followed by two defects and to finish three has variable locations. The results obtained give the designs of magneto photonic crystal devices.

2. STRUCTURE DESIGN

The 1D MPCs structure is very favored for studying the properties of photonic bandgaps, it gives a large opening bandgap and it is a good compromise, especially for high slaughter factors and the incidence angle [25, 26]. The MPCs 1D studied and analyzed in the present work, consists of a multilayer structure in periodic lattice

substrate. Unlike conventional techniques, high temperature is not required to achieve magnetic behavior. The purpose of this study is to provide a framework, is to describe the latest improvements of the approach used to develop magneto-optical structures with a wavelength of the order of (1550 nm). The advantage of this technique is the total compatibility of the sol–gel coating with the conventional integrated treatment technologies and in particular the technology on the ion exchange glass [15–18], it is considered a versatile, flexible and inexpensive technique, useful in the realization of integrated photonic systems [19–24].

¹Laboratoire d'Analyse des Signaux et Systèmes, Department of Electronics, University of M'sila, BP.166, Route Ichebilia, M'sila 28000, Algeria

²Centre de Développement des Technologies Avancées (CDTA) BP 17, Cité 20 Août 56, Baba Hassen 16303, Alger

^{*}Author to whom correspondence should be addressed. Email: mounir.bouras@univ-msila.dz

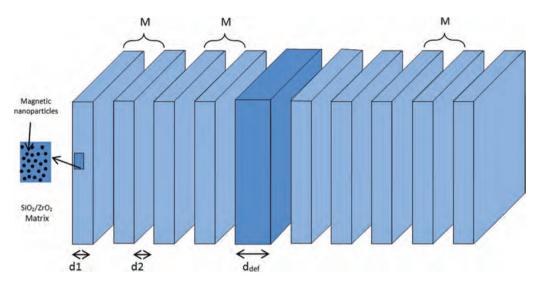


Fig. 1. Structure of 1D photonic crystal made with magneto optic layers with one defect.

 ${
m SiO_2/ZrO_2}$ or ${
m SiO_2/TiO_2}$ with air gaps, of period $a=0.70~\mu{
m m}$. The structure is characterized by a background index of 1.51 to 1.57 and an air-to-air (refractive index = 1). The thickness of the layers of material is d_1 and the gap width is d_2 with $(a=d_1+d_2)$. Figure 1 illustrates the 1D MPCs structure used for the study, it is characterized by the introduction of a defect width $(d_{
m def}=2*d_1)$ within the structure.

3. RESULTS AND DISCUSSION

In order to study the influence of the material on the photonic bandgap 1D, we introduced a defect to different

locations, then two defects and finally three. The simulation is carried out under the Rigorous Coupled Wave Analysis (RCWA) (RSoft Design Group, DiffractMode, Inc. 200 Executive Blvd. Ossining, NY 10562). Firstly, before any simulation, we are fixed geometrical parameters (number of layers 10 and the period of lattice $a=0.70~\mu m$, $a=d_1+d_2$).

In the representation of the spectral transmission curves of Figure 2, we have introduced a defect at different positions and we have observed a resonance of the value of the transmittance in the near infrared region (1500 nm to 1950 nm). The results show that the transmittance

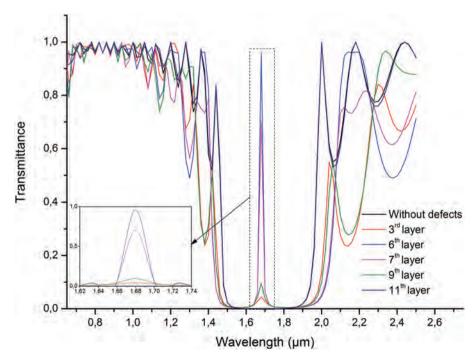


Fig. 2. Transmittance versus wavelength of 1D photonic crystal made with magneto optic layers with one defect.

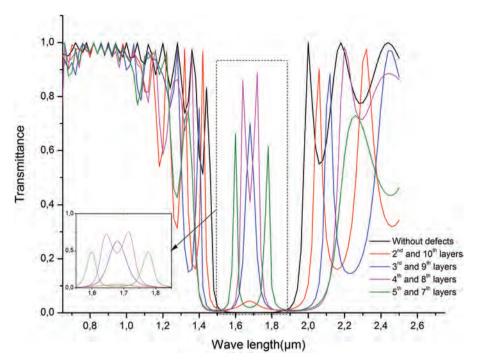


Fig. 3. Transmittance versus wavelength of 1D photonic crystal made with magneto optic layers with two defects.

varies according to the location of the defect from 0 to 0.96 [27].

Figure 2 shows the spectral response of the micro-cavity formed by defecting one layer obtained with the RCWA method of the impulse response for values of refractive index 1.51. The spectrum calculated by TM polarization can be observed one cavity mode for different

defects at different positions. From the simulated results, we observe that the best resonance value of the transmittance is obtained for the defect located in the center of the structure, namely at the 6th layer.

The results obtained for this case show us an improved transmittance compared to the results obtained in the different works carried out [28–31].

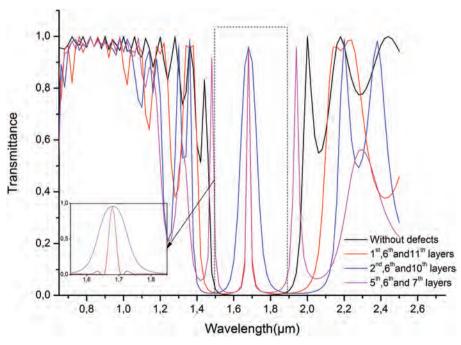


Fig. 4. Transmittance versus wavelength of 1D photonic crystal made with magneto optic layers with three defects.

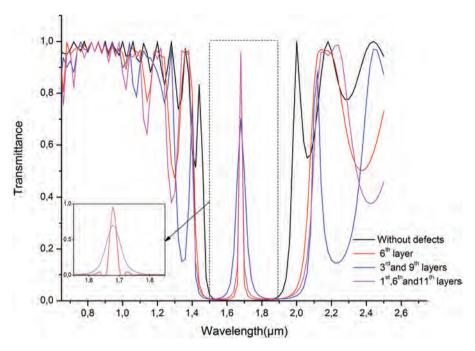


Fig. 5. Comparisons of the three structures configurations.

In the following, we study the optical properties of the behavior of one dimensional photonic bandgap when two or three defects are inserted at different locations in the structure.

A resonance of the value of the transmittance is observed in the bandgap which obtained without defects. The value of transmittance is strongly influenced by the presence of the defects and their locations. From the results obtained, we observe that the most regular value is obtained for the defects located in the third layer and ninth layer.

As seen, the structures have not only a high transmittance, but also provide the flat top resonance peaks. Therefore, these matrices doped with MPCs magnetic nanoparticles based on be used in integrated MOs, since the operating bandwidth is one of the most important functional characteristics of MPC-based devices [28–31]. Devices built on narrowband CPM would face instability due to frequency fluctuations; a flat-topped resonance is necessary in practice.

For different positions of three defects, we show in Figure 4 the simulation results of the resonant wavelength which hardly changes dependence on position of defects.

For a multi-cavity structure a significant improvement of the transmittance is obtained for a variable localization of the defects which is in adequacy with the work previously carried out [30, 31].

Now, we make a comparison of the three structures configurations used with the best values of the transmittance resonance obtained.

For a single defect, the best value corresponds to the 6th layer, then for two defects the best value is obtained for the 3rd and the 9th layer. For three defects, the best value

is obtained for the 1st, the 6th and the 11th layer like us mentioned in Figure 5. It is clear that the three configurations give good results however the first configuration (one defect at the 6th layer) remains the one that gives the best value of the resonance. Therefore, these ${\rm SiO_2/ZrO_2}$ matrix doped with ${\rm CoFe_2O_4}$ magnetic nanoparticles-based MPCs can be used in integrated MO devices such as filters and isolators.

4. CONCLUSION


This work presents a new design for magneto-photonic crystal platform cavity. We have utilized a new kind of artificial magneto optical materials (SiO₂/ZrO₂ or SiO₂/TiO₂ matrix doped with magnetic nanoparticles) in magneto-photonic crystals as a magnetic defect layer, characterized by low refractive index material 1.51. In addition, we have studied the effect of the defects at different locations on the resonance of the value of the transmittance of microcavities in a one dimensional magneto-photonic crystal. The resonance of the value of the transmittance in the bandgap is sensitive to the locations and number of photonic crystal cavity. Hence, we have also investigated the influence of defects at different locations on the optical response of transmission-type one-dimensional MPCs.

References and Notes

- Uhlmann, D.R., Teowee, G. and Boulton, J., 1997. The future of sol-gel science and technology. *Journal of Sol-Gel Science* and Technology, (8), pp.1083–1091.
- Hocini, A., Bouras, M. and Amata, H., 2013. Theoretical investigations on optical properties of magneto-optical thin film on ion-exchanged glass waveguide. Optical Materials, 35(9), pp.1669–1674.

- Salleh, S., Abdul Amir, H., Kumar Tiwari, A. and PienChee, F., 2016. Collision cascade and spike effects of X-ray irradiation on optoelectronic devices. *ActaPhysicaPolonica A*, 130(1), pp.93–97.
- **4.** Bouras, M. and Hocini, A., **2016**. Mode conversion in magnetooptic rib waveguide made by silica matrix doped with magnetic nanoparticles. *Optics Communications*, *363*, pp.138–144.
- Ustundağ, M. and Aslan, M., 2015. Electronic and magnetic properties of Ca-doped Mn-ferrite. ActaPhysicaPolonica A, 130, pp.362–364.
- Dötsch, H., Bahlmann, N., Zhuromsky, O., Hammer, M., Wilkens, L., Gerhardt, R., Hertel, P. and Popkov, A., 2005. Applications of magneto-optical waveguides in integrated optics. *Journal of the Optical Society of America B*, 22(1), pp.240–253.
- Yamauchi, J., Takahashi, G. and Nakano, H., 1998. Full-vectorial beam-propagation method based on the McKee-Mitchellscheme with improved finite-difference formulas.
 Journal of Light Wave Technology, 16(12), pp.2458–2464.
- Royer, F., Jamon, D., Broquin, J.-E., Amata, H., Kekesi, R., Neveu, S., Blanc-Mignon, M.-F. and Ghibaudo, E., 2011. Fully Compatible Magnetooptical Sol–Gel Material with Glass Waveguides Technologies: Application to Mode Converters. Proceedings of SPIE, Vol. 7941, pp.1–8.
- 9. Hocini, A., et al., 2013. Birefringence properties of magnetooptic rib waveguide as a function of refractive index. *J. Comput. Electron.*, 12(1), pp.50–55.
- Hocini, A., Boumaza, T., Bouchemat, M., Choueikani, F., Royer, F. and Rosseau, J.J., 2010. Modeling and analysis of birefringence in magnetoptical thin film made by SiO₂/ZrO₂ doped with ferrite of cobalt. *Appl. Phys. B*, 99(3), pp.553–558.
- **11.** Levy, M., Jalali, A.A. and Huang, X., **2009**. Magnetophotonic crystals: Nonreciprocity, birefringence and confinement. *J. Mater. Sci.*, *20*, pp.43–47.
- 12. Amata, H., Royer, F., Choueikani, F., Jamon, D., Parsy, F., Broquin, J.E., Neveu, S. and Rousseau, J.J., 2011. Hybrid magneto-optical mode converter made with a magnetic nanoparticles-doped SiO₂/ZrO₂ layer coated on an ion exchanged glass waveguide. Applied Physics Letters, 99(25), p.251108.
- Shimizu, H. and Tana, M., 2002. Formation of planar super lattice states in new grid-inserted quantum well structures. *Journals Applied Physics Letters*, 81, pp.5246–5248.
- **14.** Zamman, T.R., Guo, X. and Ram, R.J., **2005**. Predicting performance under stressful conditions using galvanic skin response. *Journal of Lightwive Technology*, *26*(2), pp.291–301.
- Aktas, B., Albaskara, M., Yalcinband, S. and Dogruc, K., 2016. Optical properties of soda-lime-silica glasses doped with eggshell powder. ActaPhysicaPolonica A, 132, pp.442–444.
- Kekesi, R., Royer, F., Jamon, D., Blanc Mignon, M.F., Abou-Diwan, E., Chatelon, J.P., Neveu, S. and Tombacz, E., 2013. 3D magneto-photonic crystal made with cobalt ferrite nanoparticles silica composite structured as inverse opal. *Opt. Mater. Express*, 3, pp.935–947.

- Royer, F., Jamon, D., Rousseau, J.J., Roux, H., Zins, D. and Cabuil, V., 2005. Magneto-optical nanoparticle-doped silica-titania planar waveguides. J. Lightwave. Technol., 86, p.011107.
- **18.** Inoue, M., et al., **2013**. *Magnetophotonics: From Theory to Applications*. Springer, Vol. 178.
- **19.** Inui, C., Tsuge, Y., Kura, H., Fujihara, S., Shiratori, S. and Sato, T., **2008**. Preparation of one-dimensional photonic crystals by sol–gel process for magneto-optical materials. *Thin Solid Films*, *516*, pp.2454–2459.
- Gonçalves, M.C., Brás, J. and Almeida, R.M., 2007. Process optimization of sol–gel derived colloidal photonic crystals. J. Sol–Gel Sci. Techn., 42, pp.135–143.
- Kekesi, R., Royer, F., Blanc Mignon, M.F., et al., 2010. Preliminary Studies of 3D Magnetophotonic Crystals Designed from a Template Stuffed by Sol–Gel Process. *Proceedings of SPIE*, Vol. 7713, p.7713.
- 22. Choueikani, F., Royer, F., Douadi, S., Skora, A., Jamon, D., Blanc, D. and Siblini, A., 2009. Low birefringent magnetooptical waveguides fabricated via organic-inorganic solgel process. *Journal of Applied Physics*, 47, p.30401.
- 23. Royer, F., Jamon, D., Broquin, J.E., Amata, H., Kekesi, R., Neveu, S., Mignon, M.F.B. and Ghibaudo, E., 2011. Fully Compatible Magneto-Optical Sol–Gel Material with Glass Waveguides Technologies: Application to Mode Converters. *Proc. SPIE*, Vol. 7941, pp.794106–794114.
- Amata, H., Royer, F., Choueikani, F., Jamon, D., Broquin, J.E., Plenet, J.C. and Rousseau, J.J., 2011. Magnetic Nanoparticles Doped Silica Layer Reported on Ionexchanged Glass Waveguide. *Proc. SPIE*, Vol. 7719, p.853693.
- **25.** Kahlouche, A., Hocini, A. and Khedrouche, D., **2014.** Bandgap properties of 2D photonic crystal made by silica matrix doped with magnetic nanoparticles. *Journal of Computational Electronics*, *13*, pp.490–495.
- Kuang, W., Hou, Z., Liu, Y. and Li, H., 2005. The band gap of a photonic crystal with triangular dielectric rods in a honeycomb lattice. *Journal of Optics. A: Pure and Applied Optics*, 7, pp.525–528.
- Inoue, M., Fujikawa, R., Baryshev, A., Khanikaev, A., Lim, P.B., Uchida, H., Aktsipetrov, O., Fedyanin, A., Murzina, T. and Granovsky, A., 2006. J. Phys. D, 39, p.R151.
- Zamani, M. and Ghanaatshoar, M., 2012. Adjustable magnetooptical isolators with flattop responses. Optics Express, 20, pp.24524–24535.
- Kekesi, R., Royer, F., Jamon, D., Mignon, M.B., Abou-Diwan, E., Chatelon, J., Neveu, S. and Tombacz, E.,
 2013. Optical Materials Express, 3, p.935.
- 30. Abou Diwan, E., Royer, F., Jamon, D. and Kekesi, R., 2016. Large spectral modification of the faraday effect of 3D SiO₂/CoFe₂O₄ magneto-photonic crystals. *Journal of Nanoscience and Nanotechnology*, 16(9), pp.1–6.
- Mehdi Zamani, 2016. Photonic crystal-based optical filters for operating in second and third optical fiber windows. Superlattices and Microstructures, 92, pp.157–765.

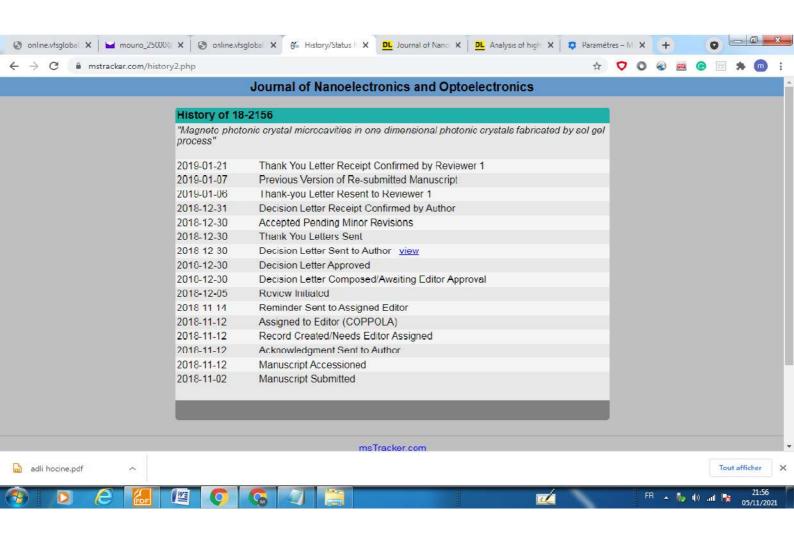



Journal of Nanoelectronics and Optoelectronics COPYRIGHT TRANSFER AGREEMENT

In order to expedite the publication process, the transfer of copyright from the contributor(s) should be clearly stated to enable American Scientific Publishers (ASP) to disseminate your work to the fullest extent. The following copyright transfer must be signed and returned to the American Scientific Publishers, 26650 The Old Road, Suite 208, Valencia, California 91381, USA, as soon as possible after the manuscript is accepted for publication. The copyright to the unpublished and original research article, including copyright to the cover illustration, abstract forming part thereof should be transferred. By signing this agreement, the contributors (authors) warrant that the entire work is original and unpublished; it is submitted only to this Journal and all text, data, figures/tables or other illustrations included in this work are completely original and unpublished, and these have not been previously published or submitted elsewhere in any form or media whatsoever. Each author(s) agree to transfer all copyrights of this work to the Journal.

Manuscript Title: Magneto-photonic crystal microcavities in one dimensional photonic crystals fabricated by sol gel process

Contributor(s): Dermeche Nassim, Bouras Mounir, Ahmed Kahlouche

is hereby transferred and assigned to American Scientific Publishers for the full term of exclusive copyright and any extensions or renewals of that terms thereof throughout the world, including but not limited to publish, disseminate, transmit, store, translate, distribute, sell, republish and use the Contribution and material contained therein in print and electronic form of the journal and in other derivative works, in all languages and any form of media of expression available now or in the future and to license or permit others to do so.

(I) The contributor(s) explicitly reserve the following rights:

(a) All proprietary rights other than copyright, such as patent rights.

- (b) Make photocopies of his/her own work for his/her own classroom teaching and research purposes, and use part of the article and abstract, without revision or modification in own personal compilations provided that (i) such print copies and works are not resold or disseminated by authors and any other recipient parties where recipients are informed that no further photocopying or dissemination of Article is allowed and (ii) reference to the original source of publication and the name of the American Scientific Publishers as copyright holder is clearly stated on any use made of the article. (iii) Contributors should not post the Article on open websites or disseminate through an internet to anyone whatsoever.
- (c) The right to use, figures/tables or other illustrations of Article (no text) in subsequent publications of the authors owns works provided that written permission is obtained from Publisher and that a proper acknowledgment is made to the original source of publication and to the Publisher.

(d) Any other use or reproduction in a collective work requires a fee and permission from Publisher.

- (e) The right to grant or refuse permission to third parties to republish part of the article or translations thereof. However, the publisher except at the direction of the contributor(s) will not refuse such permission.
- (f) American Scientific Publishers reserves the right to use all figures on any of its publication covers from the submitted manuscript. Each author(s) also grants American Scientific Publishers the rights to use his or her name and all biographical data in the article for its or the journal's promotion.
- (2) If the article has been prepared by an employee within the duration of his or her employment, the employer reserves the right to make copies of the Work in print format for its own internal use or for promotional purposes only provided that proper reference is made to the original source of publication and to the Publisher. If the manuscript has been prepared as a work made for hire, both employer and employee should sign the copyright transfer.
- (3) If the article was prepared under the U.S. Government contract, the transfer of copyright is effective to the extent that such copyright is transferable.

Each contributor(s) warrants that his or her research institution has fully approved the protocol for all scientific studies involving animals or humans and that all experiments of any kind were conducted in compliance with ethical and humane principles of researchafter approval.

The contributor(s) warrant that the work contains no unlawful or libelous statements and opinions and liable materials of any kind whatsoever, does not infringe on any copyrights, intellectual property rights, personal rights or rights of any kind of others, nor contains any plagiarized, fraudulent, improperly attributed materials, instructions, procedures, information or ideas that might cause any harm, damage, injury, losses or costs of any kind to person or property. The contributor(s) also represent and warrant that they have full power and authority to enter into this Agreement. All contributors are fully responsible for the complete contents of the manuscript Each contributor(s) agrees to defend, indemnify, and hold harmless American Scientific Publishers and the Editors for any breach of warranties under this agreement. The undersigned hereby transfer the exclusive copyright interests in the above cited manuscript to the American Scientific Publishers, with the consent of all contributors.

Whenever publisher is contacted by third parties for individual permissions to use in a collective work, reprint for library reserve or classroom or otherwise, the undersigned Contributor's or employer's permissions will also be required.

This agreement should be signed by the Contributor(s) or in the case of multiple contributors, by at least one of the contributors who agrees to inform other co-contributors the full terms of this agreement and have their full permission to sign on their behalf.

Contributor's Own Work (Author(s), please tick mark kind of your w	Work made for hire for Employer Cork)	U. S. Government Work
Laboratoire d'Analyse des Signaux et Systèmes, Department of Electronics, University of M'sila, BP.166, Route Ichebilia, M'sila 28000, Algeria.		
Name of Employer & Address (Institution/C	Company)	
Ahmed Kahlouche		
Contributor's Name & Title (Print)		

Contributor's Signature

25/02/2019 Date